

Public-law institution jointly founded by the federal states and the Federation

European Technical Assessment Body
for construction products



European Technical Assessment

ETA-22/0001
of 30 October 2024

English translation prepared by DIBt - Original version in German language

General Part

Technical Assessment Body issuing the European Technical Assessment:

Deutsches Institut für Bautechnik

Trade name of the construction product

fischer injection system FIS EM Plus

Product family
to which the construction product belongs

Post-installed reinforcing bar (rebar) connections with improved bond-splitting behaviour

Manufacturer

fischerwerke GmbH & Co. KG
Otto-Hahn-Straße 15
79211 Denzlingen
DEUTSCHLAND

Manufacturing plant

This European Technical Assessment contains

20 pages including 3 annexes which form an integral part of this assessment

This European Technical Assessment is issued in accordance with Regulation (EU) No 305/2011, on the basis of

EAD 332402-00-0601, Edition 09/2023

This version replaces

ETA-22/0001 issued on 31 July 2023

The European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and shall be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may only be made with the written consent of the issuing Technical Assessment Body. Any partial reproduction shall be identified as such.

This European Technical Assessment may be withdrawn by the issuing Technical Assessment Body, in particular pursuant to information by the Commission in accordance with Article 25(3) of Regulation (EU) No 305/2011.

Specific Part

1 Technical description of the product

The subject of this European Technical Assessment is the post-installed connection, by anchoring or overlap connection joint, of reinforcing bars (rebars) in existing structures made of normal weight concrete, using the fischer injection system FIS EM Plus in accordance with the regulations for reinforced concrete construction.

Reinforcing bars with a diameter ϕ from 8 to 40 mm according to Annex A and the injection mortar FIS EM Plus are used for the post-installed rebar connection. The rebar is placed into a drilled hole filled with injection mortar and is anchored via the bond between embedded reinforcing bar, injection mortar and concrete.

The product description is given in Annex A.

2 Specification of the intended use in accordance with the applicable European assessment Document

The performances given in Section 3 are only valid if the rebar connection is used in compliance with the specifications and conditions given in Annex B.

The verifications and assessment methods on which this European Technical Assessment is based lead to the assumption of a working life of the rebar connections of at least 50 and/or 100 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

3 Performance of the product and references to the methods used for its assessment

3.1 Mechanical resistance and stability (BWR 1)

Essential characteristic	Performance
Characteristic resistance to tension load (static and quasi-static loading)	See Annexes C1 to C3
Characteristic resistance to tension load (seismic loading)	See Annex C4

3.2 Safety in case of fire (BWR 2)

Essential characteristic	Performance
Reaction to fire	Class A1

4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base

In accordance with European Assessment Document EAD No. 332402-00-0601, the applicable European legal act is: [96/582/EC].

The system to be applied is: 1

5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable European Assessment Document

Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited with Deutsches Institut für Bautechnik.

Issued in Berlin on 30 October 2024 by Deutsches Institut für Bautechnik

Beatrix Wittstock
Head of Section

beglaubigt:
Stiller

Installation conditions and application examples reinforcing bars

Figure A1.1:

Column / wall to foundation / slab

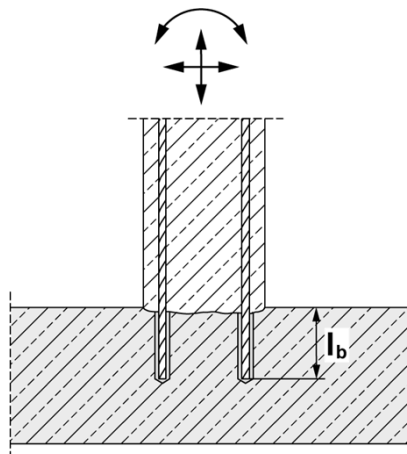
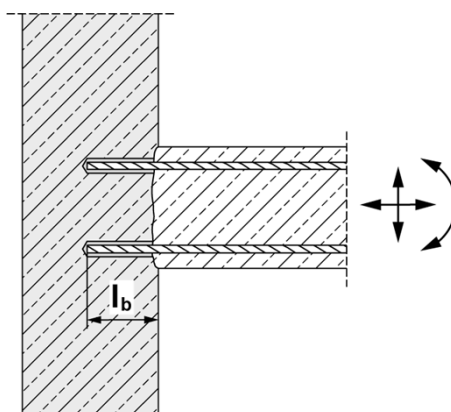


Figure A1.2:

Slab / beam to wall or beam to column



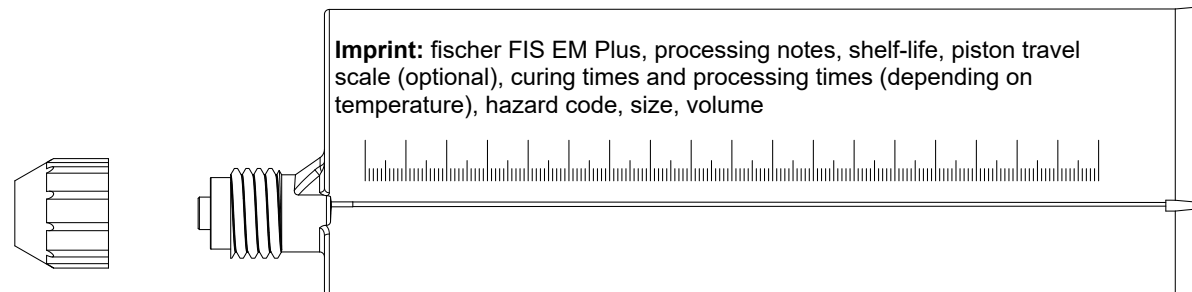
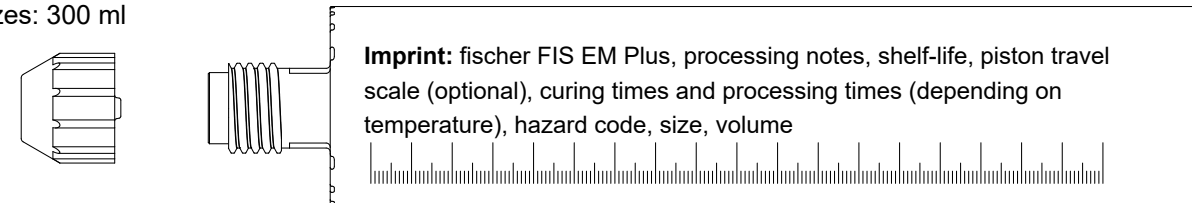





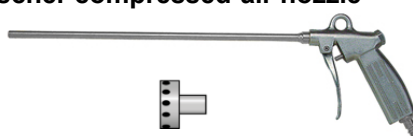
Figures not to scale

fischer injection system FIS EM Plus

Product description

Installation conditions and application examples reinforcing bars

Annex A1

<p>Overview system components</p>	
<p>Injection cartridge (shuttle cartridge) FIS EM Plus with sealing cap Sizes: 390 ml, 585 ml, 1100 ml, 1500 ml</p>  <p>Imprint: fischer FIS EM Plus, processing notes, shelf-life, piston travel scale (optional), curing times and processing times (depending on temperature), hazard code, size, volume</p>	
<p>Injection cartridge (coaxial cartridge) FIS EM Plus with sealing cap Sizes: 300 ml</p>  <p>Imprint: fischer FIS EM Plus, processing notes, shelf-life, piston travel scale (optional), curing times and processing times (depending on temperature), hazard code, size, volume</p>	
<p>Static mixer FIS MR Plus for injection cartridges 300 ml and 390 ml</p> 	
<p>Static mixer FIS UMR for injection cartridges ≥ 585 ml</p> 	
<p>Injection adapter and extension tube Ø 9 for static mixer FIS MR Plus; Injection adapter and extension tube Ø 9 or Ø 15 for static mixer FIS UMR</p> 	
<p>Reinforcing bar (rebar) Sizes: φ8, φ10, φ12, φ14, φ16, φ20, φ22, φ24, φ25, φ26, φ28, φ30, φ 32, φ34, φ36, φ40</p> 	
<p>fischer cleaning brush</p> 	
<p>Compressed-air cleaning tool with fischer compressed-air nozzle</p> 	
<p>Figures not to scale</p>	
<p>fischer injection system FIS EM Plus</p>	
<p>Product description Overview system components: injection mortar, static mixer, injection adapter, reinforcing bar, cleaning tools</p>	<p>Annex A2</p>

Properties of reinforcing bars (rebar)

Figure A3.1:



- The minimum value of related rib area $f_{R,min}$ according to EN 1992-1-1:2004+AC:2010
- The maximum outer rebar diameter over the ribs shall be:
 - The nominal diameter of the bar with rib $\phi + 2 \cdot h_{rib}$ ($h_{rib} \leq 0,07 \cdot \phi$)
 - (ϕ : Nominal diameter of the bar; h_{rib} = rib height of the bar)

Table A3.1: Installation conditions for rebars




Nominal diameter of the bar		ϕ	8 ¹⁾	10 ¹⁾	12 ¹⁾	14	16	20	22	24	
Nominal drill hole diameter	d_0	[mm]	10	12	14	16	18	20	25	30	
Drill hole depth	h_0		$h_0 \geq l_b$								
Effective embedment depth	$l_b = l_v$		acc. to static calculation								
Minimum thickness of concrete member	h_{min}		$l_b + 30$ (≥ 100)			$l_b + 2d_0$					

Nominal diameter of the bar		ϕ	25 ¹⁾	26	28	30	32	34	36	40	
Nominal drill hole diameter	d_0	[mm]	30	35	35	40	40	40	45	55	
Drill hole depth	h_0		$h_0 \geq l_b$								
Effective embedment depth	$l_b = l_v$		acc. to static calculation								
Minimum thickness of concrete member	h_{min}		$l_b + 2d_0$								

¹⁾ Both drill hole diameters can be used

Table A3.2: Materials of rebars

Designation	Reinforcing bar (rebar)
Reinforcing bar EN 1992-1-1:2004+AC:2010, Annex C	Bars and de-coiled rods class B or C with f_{yk} and k according to NDP or NCI of EN 1992-1-1/NA $f_{uk} = f_{tk} = k \cdot f_{yk}$
fischer injection system FIS EM Plus	Annex A3
Product description Properties and materials of reinforcing bars (rebar)	

Specifications of intended use part 1			
Table B1.1: Overview use and performance categories			
Fastenings subject to		FIS EM Plus with ...	
		Reinforcing bar 	
Hammer drilling with standard drill bit		all sizes	
Hammer drilling with hollow drill bit (fischer "FHD", Heller "Duster Expert"; Bosch "Speed Clean"; Hilti "TE-CD, TE-YD", DreBo "D-Plus", DreBo "D-Max")		Nominal drill bit diameter (d_0) 12 mm to 35 mm	
Use category	I1 dry or wet concrete	all sizes	
	I2 water filled hole	all sizes	
Characteristic resistance under static and quasi-static loading	in uncracked concrete	all sizes	Tables: C1.1 C1.2 C2.1 C3.1
	in cracked concrete	all sizes	
Seismic performance		all sizes	Table: C4.1
Installation direction	D3 (downward and horizontal and upwards (e.g. overhead))		
Installation temperature	$T_{i,min} = -5\text{ °C}$ to $T_{i,max} = +40\text{ °C}$ for the standard variation of temperature after installation		
In-service temperature	Temperature range I	-40 °C to +40 °C	(max. short term temperature +40 °C; max. long term temperature +24 °C)
	Temperature range II	-40 °C to +60 °C	(max. short term temperature +60 °C; max. long term temperature +35 °C)
	Temperature range III	-40 °C to +72 °C	(max. short term temperature +72 °C; max. long term temperature +50 °C)
fischer injection system FIS EM Plus			Annex B1
Intended use Specifications part 1			

Specifications of intended use part 2

Anchorage subject to:

- Static and quasi-static loading: reinforcing bar (rebar) size 8 mm to 40 mm
- Seismic action: reinforcing bar (rebar) size 8 mm to 40 mm

Base materials:

- Compacted reinforced or unreinforced normal weight concrete without fibres according to EN 206:2013+A2:2021.
- Strength classes C20/25 to C50/60 according to EN 206:2013+A2:2021
- Maximum chloride content of 0,40 % (CL 0.40) related to the cement content according to EN 206:2013+A2:2021
- Non-carbonated concrete

Note: In case of a carbonated surface of the existing concrete structure, the carbonated layer shall be removed in the area of the post-installed rebar connection with a diameter of $\phi + 60$ mm prior to the installation of the new rebar. The depth of concrete to be removed shall correspond to at least the minimum concrete cover in accordance with EN 1992-1-1 :2004+AC:2010. The foregoing may be neglected if building components are new and not carbonated and if building components are in dry conditions.

Design:

- The structural design according to EN 1992-1-1:2011, EN 1992-1-2:2011 and Annex B3 and B4 are conducted under responsibility of a designer experienced in the field of anchorages and concrete works.
- Verifiable calculation notes and drawings are prepared taking account of the forces to be transmitted.
- Design under static and quasi-static loading and for seismic actions in accordance with EOTA Technical Report TR 069 June 2021.
- The actual position of the reinforcement in the existing structure shall be determined on the basis of the construction documentation and taken into account when designing.
- The shear force must be transferred via the rough joint; the subsequent reinforcement must not be applied for shear force transfer.

Installation:

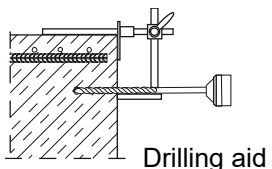
- Rebar installation carried out by appropriately qualified personnel and under the supervision of the person responsible for technical matters of the site.
- Check the position of the existing rebars (if the position of existing rebars is not known, it shall be determined using a rebar detector suitable for this purpose as well as on the basis of the construction documentation and then marked on the building component for the overlap joint).
- Rebars in overhead installation have to be fixed in their position until the injection mortar is cured.

fischer injection system FIS EM Plus

Intended use
Specifications part 2

Annex B2

Table B3.1: Minimum concrete cover c_{min} ¹⁾ depending on the drilling method and the drilling tolerance²⁾

Drilling method	nominal diameter of reinforcing bar ϕ [mm]	Minimum concrete cover c_{min}		
		Without drilling aid [mm]	With drilling aid [mm]	
Hammer drilling with standard drill bit	< 25	30 mm + 0,06 $l_b \geq 2 \phi$	30 mm + 0,02 $l_b \geq 2 \phi$	
	≥ 25	40 mm + 0,06 $l_b \geq 2 \phi$	40 mm + 0,02 $l_b \geq 2 \phi$	
Hammer drilling with hollow drill bit (fischer "FHD", Heller "Duster Expert"; Bosch "Speed Clean"; Hilti "TE-CD, TE-YD")	< 25	30 mm + 0,06 $l_b \geq 2 \phi$	30 mm + 0,02 $l_b \geq 2 \phi$	
	≥ 25	40 mm + 0,06 $l_b \geq 2 \phi$	40 mm + 0,02 $l_b \geq 2 \phi$	

¹⁾ Note: The minimum concrete cover as specified in EN 1992-1-1:2004+AC:2010 must be observed.

²⁾ Minimum clear spacing is $a = \max(40 \text{ mm}; 4 \cdot \phi)$

Table B3.2: Dispensers and cartridge sizes corresponding to maximum embedment depth $l_{b,max}$

reinforcing bars (rebar)	Manual dispenser	Pneumatic or cordless dispenser (small)	Pneumatic or cordless dispenser (large)	
	Cartridge size 300 ml, 390 ml, 585 ml	Cartridge size 300 ml, 390 ml, 585 ml	Cartridge size 1500 ml	
ϕ [mm]	$l_{b,max}$ [mm]	$l_{b,max}$ [mm]	$l_{b,max}$ [mm]	
8	1000	1000	1800	
10		1200		
12				1500
14				
16		700		1300 ¹⁾
20	1000 ¹⁾			
22 / 24 / 25	500	700 ¹⁾		
26 / 28		500 ¹⁾		
30 / 32 / 34	no performance assessed		500 ¹⁾	
36 / 40				

¹⁾ Not possible with the 300 ml cartridge

Figures not to scale

fischer injection system FIS EM Plus

Intended use

Minimum concrete cover;
dispenser and cartridge sizes corresponding to maximum embedment depth

Annex B3

Table B4.1: Conditions for use static mixer without an extension tube															
Nominal drill hole diameter	d_0	[mm]	10	12	14	16	18	20	24	25	28	30	35	40	
Drill hole depth h_0 by using	FIS MR Plus		≤ 90		≤ 120	≤ 140	≤ 150	≤ 160	≤ 190	≤ 210					
	FIS UMR		-	-	≤ 90	≤ 160	≤ 180	≤ 190	≤ 220		≤ 250				
Table B4.2: Working times t_{work} and curing times t_{cure}															
Temperature at anchoring base [°C]		Maximum processing time ¹⁾ t_{work}					Minimum curing time ²⁾ t_{cure}								
-5 to 0		240 min ³⁾					200 h								
>0 to 5		150 min ³⁾					90 h								
>5 to 10		120 min ³⁾					40 h								
>10 to 20		30 min					18 h								
>20 to 30		14 min					10 h								
>30 to 40		7 min ⁴⁾					5 h								
¹⁾ Maximum time from the beginning of the injection to the setting and the final positioning of the rebar ²⁾ For wet concrete the curing time must be doubled ³⁾ If the temperature in the concrete falls below 10 °C the cartridge must be warmed up to +15 °C. ⁴⁾ If the temperature in the concrete exceeds 30 °C the cartridge must be cooled down to +15 °C up to 20 °C															
Table B4.3: Installation tools for drilling and cleaning the bore hole and injection of the mortar															
reinforcing bars (rebar)	Drilling and cleaning				Injection										
	Nominal drill bit diameter d_0 [mm]	Diameter of cutting edge d_{cut} [mm]	Steel brush diameter d_b [mm]	Diameter of cleaning nozzle ³⁾ [mm]	Diameter of extension tube [mm]	Injection adapter [colour]									
ϕ [mm]	8 ¹⁾	10 ²⁾	$\leq 10,50$	11	---	---									
	10 ¹⁾	12	$\leq 12,50$	14	11	nature									
14		$\leq 14,50$	16	blue											
12 ¹⁾	14	$\leq 14,50$	16	15	red										
	16	$\leq 16,50$	20		yellow										
14	18	$\leq 18,50$	20	19	green										
16	20	$\leq 20,55$	25		black										
20	25	$\leq 25,55$	27		grey										
22 / 24	30	$\leq 30,55$	32	28	grey										
		$\leq 30,55$	32		grey										
25 ¹⁾	35	$\leq 35,70$	37	9 or 15	brown										
26 / 28	35	$\leq 35,70$	37		brown										
	30 / 32 / 34	40 ²⁾	$\leq 40,70$		42	red									
36	45 ²⁾	$\leq 45,70$	47	38	yellow										
40	55 ²⁾	$\leq 55,70$	58		nature										
¹⁾ Both drill bit diameters can be used ²⁾ Only hammer drilling with standard drill bit ³⁾ Cleaning nozzle and extension is only necessary if bore hole depth is greater than the length of compressed-air cleaning tool															
fischer injection system FIS EM Plus											Annex B4				
Intended use Conditions for use static mixer without an extension tube; Working times and curing times; Installation tools for drilling and cleaning the bore hole and injection of the mortar															

Safety regulations

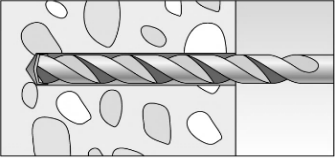
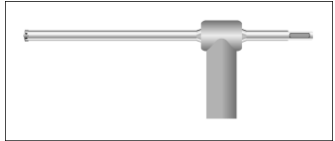
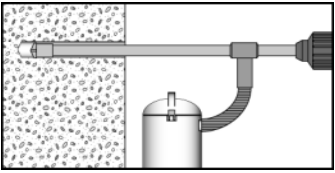
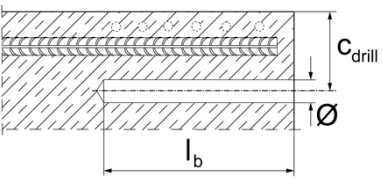
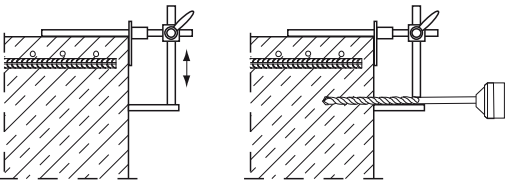


Review the Safety Data Sheet (SDS) before use for proper and safe handling!
Wear well-fitting protective goggles and protective gloves when working with mortar FIS EM Plus.
Important: Observe the instructions for use provided with each cartridge.

Installation instruction part 1

Hole drilling

Note: Before drilling, remove carbonated concrete; clean contact areas (see Annex B2)
In case of aborted drill holes the drill hole shall be filled with mortar.

1a	<p>Hammer drilling with standard drill bit</p> 	<p>Drill the hole to the required embedment depth using a hammer drill with carbide drill bit set in rotation hammer mode. Nominal drill hole diameter d_0 (see table B4.3) and drill hole depth h_0 (see table A3.1).</p>
1b	<p>Hammer drilling with hollow drill bit</p> 	<p>Check a suitable hollow drill (see table B1.1) for correct operation of the dust extraction.</p>
		<p>Drill the hole to the required embedment depth using a hammer drill with hollow drill bit in rotation hammer mode. Dust extraction conditions see drill hole cleaning Annex B6. Nominal drill hole diameter d_0 (see table B4.3) and drill hole depth h_0 (see table A3.1).</p>
2		<p>Measure and control concrete cover c ($c_{drill} = c + \varnothing / 2$) Drill parallel to surface edge and to existing rebar. Where applicable use fischer drilling aid.</p>
		<p>For holes $l_b > 20$ cm use drilling aid. Three different options can be considered: A) fischer drilling aid B) Stat or spirit level C) Visual check</p> <p>Minimum concrete cover c_{min} see table B3.1.</p>

fischer injection system FIS EM Plus

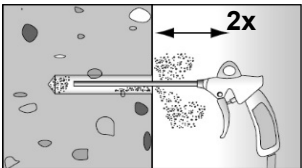

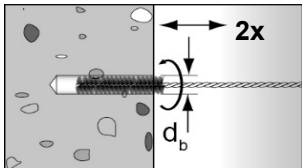
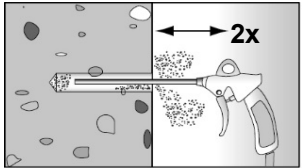

Intended use

Safety regulations; Installation instruction part 1, hole drilling

Annex B5

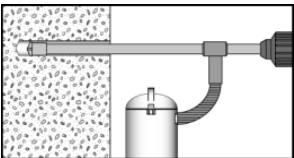
Installation instruction part 2

Drill hole cleaning (hammer drilling with standard drill bit)

		<p>Cleaning the drill hole. Blow out the drill hole twice, with oil free compressed air ($p \geq 6$ bar). If the drill hole depth is greater than the length of the compressed-air cleaning tool, an extension and appropriate fischer cleaning nozzle must be used. Corresponding diameters see table B4.3.</p>	
<p>3a</p>		<p>Brush the drill hole twice. For drill hole diameter ≥ 30 mm use a power drill. For deep holes use an extension. Corresponding brushes see table B4.3.</p>	
		<p>Cleaning the drill hole: Blow out the drill hole twice, with oil free compressed air ($p \geq 6$ bar). If the drill hole depth is greater than the length of the compressed-air cleaning tool, an extension and appropriate fischer cleaning nozzle must be used. Corresponding diameters see table B4.3.</p>	

Go to step 4

Drill hole cleaning (hammer drilling with hollow drill bit)

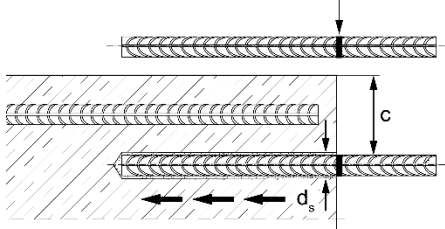
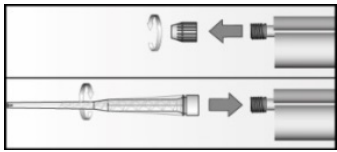
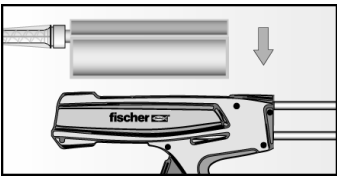
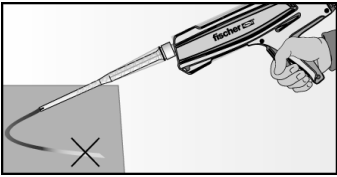
<p>3b</p>		<p>Use a suitable dust extraction system, e. g. fischer FVC 35 M or a comparable dust extraction system with equivalent performance data.</p> <p>Drill the hole with hollow drill bit. The dust extraction system has to extract the drill dust nonstop during the drilling process and must be adjusted to maximum power. Check the hollow drill for correct operation of the dust extraction. No further cleaning steps necessary.</p>
------------------	---	--

Go to step 4

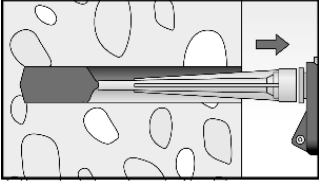
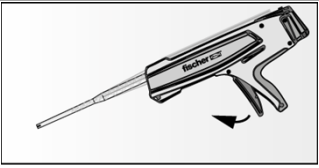
fischer injection system FIS EM Plus

Intended use
Installation instruction part 2, drill hole cleaning

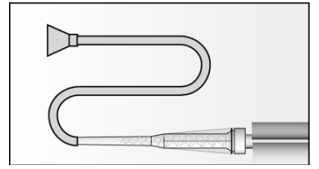
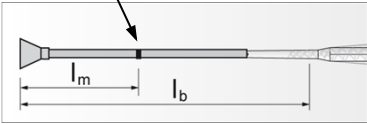
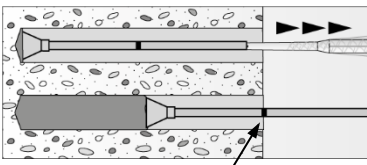
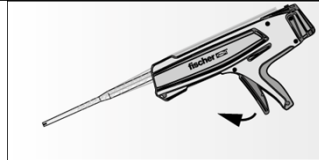
Annex B6

Installation instruction part 3 Reinforcing bars (rebar) and cartridge preparation	
4	 <p>Before use, make asure that the rebar is dry and free of oil or other residue. Mark the embedment depth l_b (e.g. with tape) Insert rebar in borehole, to verify drill hole depth and setting depth l_b.</p>
5	 <p>Twist off the sealing cap Twist on the static mixer (the spiral in the static mixer must be clearly visible).</p>
6	 <p>Place the cartridge into a suitable dispenser.</p>
7	 <p>Press out approximately 10 cm of mortar until the resin is permanently grey in colour. Mortar which is not grey in colour will not cure and must be disposed.</p>
Go to step 8	
fischer injection system FIS EM Plus	
Intended use Installation instruction part 3, reinforcing bars (rebar) and cartridge preparation	
Annex B7	

Installation instruction part 4; Installation with FIS EM Plus Injection of the mortar without extension tube

<p>8a</p>		<p>Inject the mortar from the back of the hole towards the front and slowly withdraw the static mixer step by step with each trigger pull. Avoid bubbles. Fill holes approximately 2/3 (for $h_0 = l_b$) full, to ensure that the annular gap between the rebar and the concrete will be completely filled with adhesive over the entire embedment length. For $h_0 > l_b$ more mortar is needed. The conditions for mortar injection without extension tube can be found in table B4.1</p>
		<p>After injecting, release the dispenser. This will prevent further mortar discharge from the static mixer.</p>

Injection of the mortar with extension tube

		<p>Assemble mixing nozzle FIS MR Plus or FIS UMR, extension tube and appropriate injection adapter (see table B4.3).</p>
<p>8b</p>	<p>Mortar level mark</p> 	<p>Mark the required mortar level l_m and embedment depth l_b with tape or marker on the injection extension tube. a) Estimation: $l_m = \frac{1}{3} \cdot l_b \text{ [mm]}$ b) Precise equation for optimum mortar volume: $l_m = l_b \cdot \left(\left(1,2 \cdot \frac{d_s^2}{d_b^2} - 0,2 \right) \right) \text{ [mm]}$</p>
	 <p>Mortar level mark</p>	<p>Insert injection adapter to back of the hole. Begin injection allowing the pressure of the injected adhesive mortar to push the injection adapter towards the front of the hole. Do not actively pull out! Fill holes approximately 2/3 (for $h_0 = l_b$) full, to ensure that the annular gap between the rebar and the concrete will be completely filled with adhesive over the embedment length. For $h_0 > l_b$ more mortar is needed. When using an injection adapter continue injection until the mortar level mark l_m becomes visible. Maximum embedment depth, see table B3.2.</p>
		<p>After injecting, release the dispenser. This will prevent further mortar discharge from the static mixer.</p>

Go to step 9

fischer injection system FIS EM Plus

Intended use
Installation instruction part 4, mortar injection

Annex B8





Installation instruction part 5; Installation with FIS EM Plus	
Insert rebar	
9	 <p>Insert the rebar slowly twisted into the borehole until the embedment mark is reached. Recommendation: Rotation back and forth of the reinforcement bar makes pushing easy</p>
10	 <p>After installing the rebar the annular gap must be completely filled with mortar.</p> <p>Proper installation</p> <ul style="list-style-type: none"> • Desired embedment depth is reached l_b: embedment mark at concrete surface • Excess mortar flows out of the borehole after the rebar have been fully inserted up to the embedment mark.
11	 <p>For overhead installation, support the rebar and secure it from falling till mortar started to harden, e.g. using wedges.</p>
12	 <p>Observe the working time "t_{work}" (see table B4.2), which varies according to temperature of base material. Minor adjustments to the rebar position may be performed during the working time</p> <p>Full load may be applied only after the curing time "t_{cure}" has elapsed (see table B4.2)</p>
<p>fischer injection system FIS EM Plus</p>	
<p>Intended use Installation instruction part 5, insert rebar</p>	
<p>Annex B9</p>	

Table C1.1: Characteristic resistance under tension loading for reinforcing bars																				
Size		All sizes																		
Characteristic resistance under tension loading																				
Installation factor	γ_{inst}	[-]	See Annex C2 to C3																	
Factors for the compressive strength of concrete > C20/25																				
Increasing factor ψ_c for cracked or uncracked concrete $\tau_{Rk,C(X/Y)} = \psi_c \cdot \tau_{Rk,C(20/25)}$	C25/30	[-]	1,02																	
	C30/37		1,04																	
	C35/45		1,06																	
	C40/50		1,07																	
	C45/55		1,08																	
	C50/60		1,09																	
Concrete cone failure																				
Uncracked concrete	$k_{ucr,N}$	[-]	11,0																	
Cracked concrete	$k_{cr,N}$		7,7																	
Edge distance	$c_{cr,N}$	[mm]	$1,5 \cdot l_b$																	
Spacing	$s_{cr,N}$		$3 \cdot l_b$																	
Factors for sustained tension loading																				
Temperature range			24 °C / 40 °C				35 °C / 60 °C				50 °C / 72 °C									
Factor	ψ_{sus}^0	[-]	0,77				0,60				0,48									
Factor	$\psi_{sus,100}^0$		0,77				0,60				0,71									
Table C1.2: Essential characteristics under tension loading for reinforcing bars in hammer drilled holes; uncracked or cracked concrete; working life 50 and 100 years																				
Nominal diameter of the bar		ϕ	8	10	12	14	16	18	20	22	24	25	26	28	30	32	34	36	40	
Bond-splitting failure for working life of 50 and 100 years																				
Calculation diameter		d	[mm]	8	10	12	14	16	18	20	22	24	25	26	28	30	32	34	36	40
Hammer-drilling with standard drill bit or hollow drill bit for 50 and 100 years																				
Product basic factor	A_k	[-]	4,4																	
Exponent for influence of concrete compressive strength	sp1		0,33																	
Exponent for influence of rebar diameter ϕ	sp2		0,34																	
Exponent for influence of concrete cover c_d	sp3		0,62																	
Exponent for influence of side concrete cover (c_{max} / c_d)	sp4		0,33																	
Exponent for influence of anchorage length l_b	lb1		0,68																	
fischer injection system FIS EM Plus																				
Performances Characteristic resistance under tension loading for reinforcing bars; uncracked or cracked concrete; working life 50 and 100 years															Annex C1					

Table C2.1: Characteristic resistance under tension loading for reinforcing bars in hammer drilled holes; uncracked or cracked concrete; working life 50 years

Nominal diameter of the bar		ϕ	8	10	12	14	16	18	20	22	24			
Combined pullout and concrete cone failure														
Calculation diameter	d	[mm]	8	10	12	14	16	18	20	22	24			
Uncracked concrete														
Characteristic bond resistance in uncracked concrete C20/25														
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete)														
Temperature range	I: 24 °C / 40 °C		$\tau_{Rk,ucr,50}$	[N/mm ²]	16,0	16,8	16,1	15,5	15,0	14,6	14,2	14,0	13,6	
	II: 35 °C / 60 °C				16,0	15,0	15,0	14,0	14,0	13,0	13,0	13,0	13,0	12,0
	III: 50 °C / 72 °C				15,0	14,0	14,0	13,0	13,0	12,0	12,0	12,0	12,0	12,0
Hammer-drilling with standard drill bit or hollow drill bit (water filled hole)														
Temperature range	I: 24 °C / 40 °C		$\tau_{Rk,ucr,50}$	[N/mm ²]	16,0	16,8	16,1	14,9	14,4	13,4	13,0	12,1	11,8	
	II: 35 °C / 60 °C				16,0	16,0	14,0	13,0	12,0	12,0	11,0	11,0	10,0	
	III: 50 °C / 72 °C				15,0	14,0	13,0	12,0	12,0	11,0	11,0	10,0	10,0	
Installation factors														
Dry or wet concrete		γ_{inst}	[-]	1,0										
Water filled hole				1,4										
Influence of cracked concrete on combined pullout and concrete cone failure														
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete / water filled holes)														
Factor for cracked concrete	$\Omega_{cr,03}$	[-]	0,91	0,91	0,91	0,91	0,91	0,91	0,92	0,92	0,92			
Nominal diameter of the bar		ϕ	25	26	28	30	32	34	36	40				
Combined pullout and concrete cone failure														
Calculation diameter	d	[mm]	25	26	28	30	32	34	36	40				
Uncracked concrete														
Characteristic bond resistance in uncracked concrete C20/25														
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete)														
Temperature range	I: 24 °C / 40 °C		$\tau_{Rk,ucr,50}$	[N/mm ²]	13,5	13,3	13,1	12,9	12,7	12,5	12,4	12,1		
	II: 35 °C / 60 °C				12,0	12,0	12,0	12,0	12,0	11,0	11,0	11,0		
	III: 50 °C / 72 °C				11,0	11,0	11,0	11,0	11,0	11,0	10,0	10,0		
Hammer-drilling with standard drill bit or hollow drill bit (water filled hole)														
Temperature range	I: 24 °C / 40 °C		$\tau_{Rk,ucr,50}$	[N/mm ²]	11,5	11,4	10,6	10,5	10,3	9,0	8,0	8,0		
	II: 35 °C / 60 °C				10,0	10,0	10,0	9,0	9,0	9,0	8,0	8,0		
	III: 50 °C / 72 °C				9,0	9,0	9,0	9,0	8,0	8,0	8,0	8,0		
Installation factors														
Dry or wet concrete		γ_{inst}	[-]	1,0										
Water filled hole				1,4										
Influence of cracked concrete on combined pullout and concrete cone failure														
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete / water filled holes)														
Factor for cracked concrete	$\Omega_{cr,03}$	[-]	0,92	0,92	0,92	0,92	0,93	0,93	0,93	0,93				
fischer injection system FIS EM Plus										Annex C2				
Performances Characteristic resistance under tension loading for reinforcing bars; uncracked or cracked concrete; working life 50 years														

Table C3.1: Characteristic resistance under tension loading for reinforcing bars in hammer drilled holes; uncracked or cracked concrete; working life 100 years													
Nominal diameter of the bar		ϕ	8	10	12	14	16	18	20	22	24		
Combined pullout and concrete cone failure													
Calculation diameter		d	[mm]	8	10	12	14	16	18	20	22	24	
Uncracked concrete													
Characteristic bond resistance in uncracked concrete C20/25													
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete)													
Tem- perature range	I: 24 °C / 40 °C		$\tau_{Rk,ucr,100}$	[N/mm ²]	12,0	13,8	13,2	12,7	12,3	12,0	11,6	11,5	11,2
	II: 35 °C / 60 °C				12,0	11,3	11,3	10,5	10,5	9,8	9,8	9,8	9,0
	III: 50 °C / 72 °C				8,3	8,4	8,4	8,5	8,5	7,8	7,8	7,8	7,8
Hammer-drilling with standard drill bit or hollow drill bit (water filled hole)													
Tem- perature range	I: 24 °C / 40 °C		$\tau_{Rk,ucr,100}$	[N/mm ²]	12,0	13,8	13,2	12,2	11,8	11,0	10,7	9,9	9,7
	II: 35 °C / 60 °C				12,0	12,0	10,5	9,8	9,0	9,0	8,3	8,3	7,5
	III: 50 °C / 72 °C				8,3	8,4	7,8	7,8	7,8	7,2	7,2	6,5	6,5
Installation factors													
Dry or wet concrete		γ_{inst}	[-]	1,0									
Water filled hole				1,4									
Influence of cracked concrete on combined pullout and concrete cone failure													
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete / water filled holes)													
Factor for cracked concrete		$\Omega_{cr,03}$	[-]	0,91	0,91	0,91	0,91	0,91	0,91	0,92	0,92	0,92	
Nominal diameter of the bar		ϕ	25	26	28	30	32	34	36	40			
Combined pullout and concrete cone failure													
Calculation diameter		d	[mm]	25	26	28	30	32	34	36	40		
Uncracked concrete													
Characteristic bond resistance in uncracked concrete C20/25													
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete)													
Tem- perature range	I: 24 °C / 40 °C		$\tau_{Rk,ucr,100}$	[N/mm ²]	11,1	10,9	10,8	10,6	10,5	10,3	10,1	9,9	
	II: 35 °C / 60 °C				9,0	9,0	9,0	9,0	9,0	8,3	8,3	8,3	
	III: 50 °C / 72 °C				7,2	7,2	7,2	7,2	7,2	7,2	6,5	6,5	
Hammer-drilling with standard drill bit or hollow drill bit (water filled hole)													
Tem- perature range	I: 24 °C / 40 °C		$\tau_{Rk,ucr,100}$	[N/mm ²]	9,4	9,3	8,7	8,6	8,5	6,8	6,0	6,0	
	II: 35 °C / 60 °C				7,5	7,5	7,5	6,8	6,8	6,8	6,0	6,0	
	III: 50 °C / 72 °C				5,9	5,9	5,9	5,2	5,2	5,2	5,2	5,2	
Installation factors													
Dry or wet concrete		γ_{inst}	[-]	1,0									
Water filled hole				1,4									
Influence of cracked concrete on combined pullout and concrete cone failure													
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete / water filled holes)													
Factor for cracked concrete		$\Omega_{cr,03}$	[-]	0,92	0,92	0,92	0,92	0,93	0,93	0,93	0,93		
fischer injection system FIS EM Plus													
Performances Characteristic resistance under tension loading for reinforcing bars; uncracked or cracked concrete; working life 100 years										Annex C3			

Table C4.1: Characteristic resistance under tension loading for reinforcing bars (rebars) in concrete under seismic action; working life of 50 and 100 years																				
Nominal diameter of the bar		ϕ	8	10	12	14	16	18	20	22	24	25	26	28	30	32	34	36	40	
Resistance to pull-out failure in uncracked concrete under cyclic loading for working life of 50 and 100 years																				
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete)																				
Reduction factor for pull-out Resistance under seismic action	$\alpha_{eq,p}$	[N/mm ²]	0,76										1,0							
Influence of increased crack width on resistance to pull-out failure for working life of 50 and 100 years																				
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete)																				
Factor for influence of cracked concrete	$\Omega_{cr,05}^{1)}$	[-]	0,76	0,86	0,86	0,86	0,86	0,86	0,86	0,86	0,86	0,86	0,86	0,86	0,86	0,87	0,87	0,87	0,87	0,87
	$\Omega_{cr,08}^{1)}$		0,76	0,76	0,76	0,76	0,76	0,76	0,76	0,76	0,76	0,76	0,76	0,76	0,76	0,76	0,76	0,73	0,70	0,63
Resistance to bond-splitting failure under cyclic loading for working life of 50 and 100 years																				
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete)																				
Reduction factor for bond-splitting resistance under seismic action	$\alpha_{eq,sp}$	[-]	0,94																	
<p>1) Assumed crack width in accordance with EOTA Technical Report TR 069 June 2021; Section 3.6.</p>																				
fischer injection system FIS EM Plus															Annex C4					
Performances Characteristic resistance under tension loading for reinforcing bars (rebars) in concrete under seismic action working life of 50 and 100 years																				